

Modelling high energy density supercapacitors by molecular dynamics simulations

Mathieu Salanne


PHENIX laboratory, Sorbonne University, Paris
Network on the electrochemical storage of energy (RS2E)
<http://www.energie-rs2e.com>

Forum Teratec - July 2nd, 2014

Outline


- 1 Supercapacitors
- 2 Molecular simulations
- 3 Molecular origin of supercapacitance
- 4 Conclusion

Supercapacitors: electricity storage devices

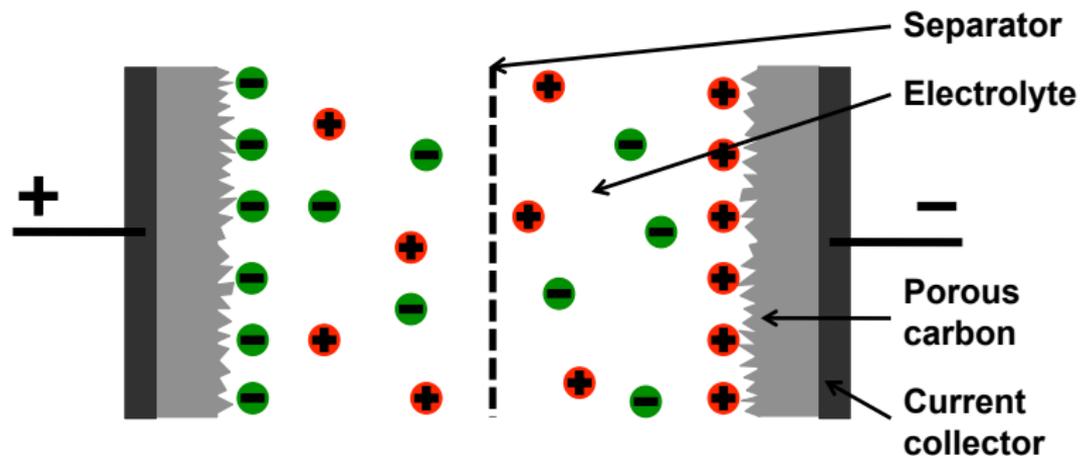

- Also called Electrochemical Double Layer Capacitors
- Charge stored through adsorption of ions at the **surface** of electrode
- No redox reaction in the bulk material → different from batteries
- $E = \frac{CU^2}{2}$ & $P = \frac{U}{4R}$

Electrode materials

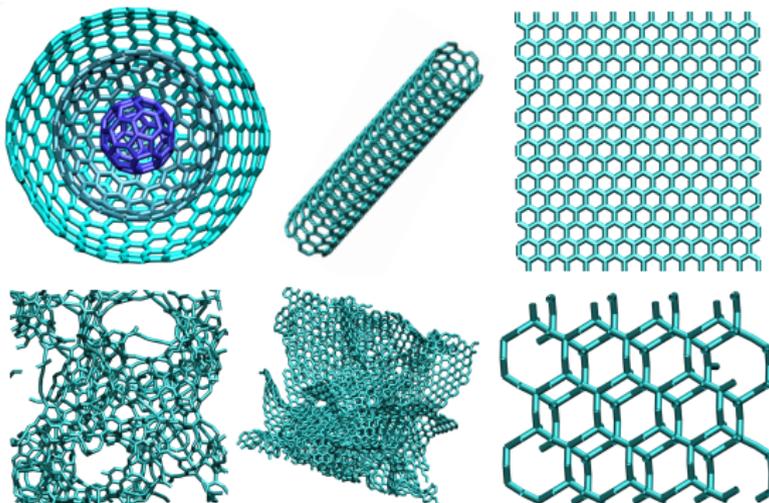

- Commercial devices: carbon materials
- 1D, 2D, 3D materials
- Various porosities, surface area, chemical activation
- Efficiency measured with the **capacitance**

Simon & Gogotsi, *Nature Materials* **7**, 845 (2008)

Electrolytes


Need to find a good compromise between:

- Large electrochemical window
- High conductivity
- Good adsorption of ions on (porous) carbon materials
- Toxicity, safety...

Depending on the application:

- Ionic liquids
- Organic electrolytes (acetonitrile + organic salts)
- Aqueous electrolytes (inorganic salts)
- Solid electrolytes (ionic liquids + polymers)

Supercapacitors in the electricity storage landscape

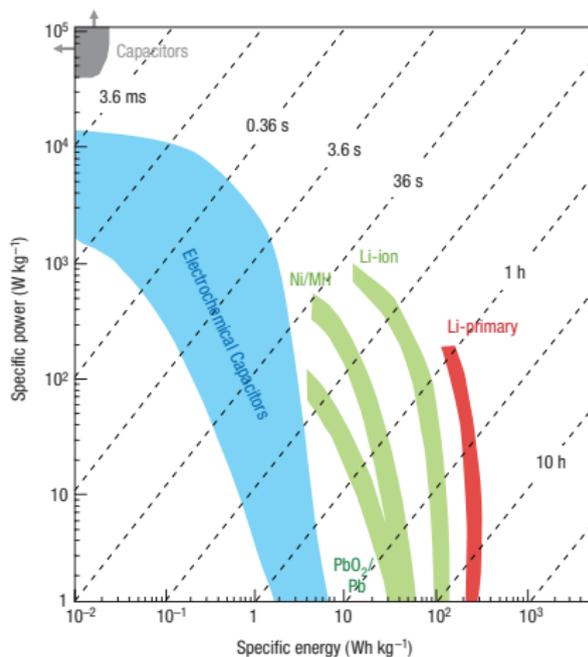


Intermediate performances between conventional capacitors and Li-ion batteries.

- High specific power
- Correct specific energy
- Rapid charge/discharge (a few seconds)
- High cyclability (1 million cycles)

Applications



Collaboration Alstom / Batscap

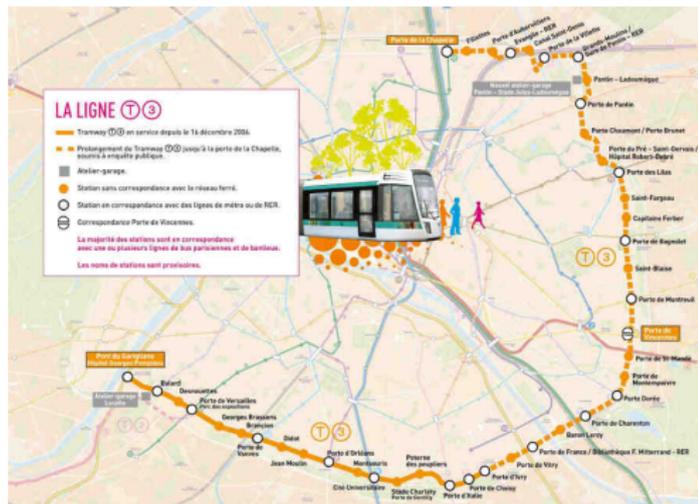

Tramway in Paris: braking energy is stored in a supercap (allows for a traction of more than 100 m)



Applications



- Peugeot 308 e-HDI: 5V supercapacitor
- Stop-start system → lower fuel consumption (-15 %)
- Also in Formula One: KERS

Experimental discovery (Gogotsi & Simon)

Carbide Derived Carbon

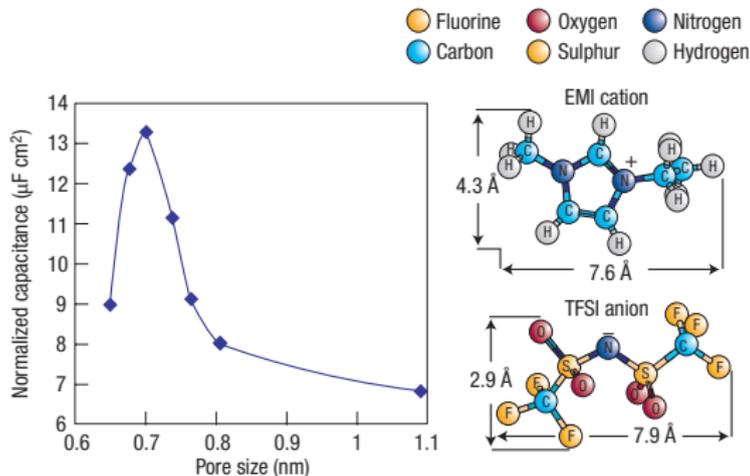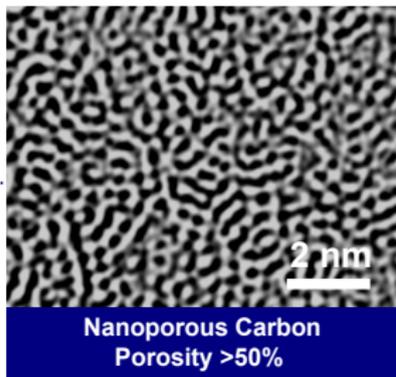

- CDC: narrow pore size distribution
- **Increase of the capacitance by +50 %!**
- Optimum when pore size = ion size


Chmiola *et al.*, *Science*, 313, 1760 (2006)

Largeot *et al.*, *J. Am. Chem. Soc.*, 130, 2730 (2008)

Challenges

Need for improvements:

- Increase of capacitance
→ design of new carbon materials
- Electrolytes with high potential window
- Electrolytes with high conductivity at low temperature (-40°C)

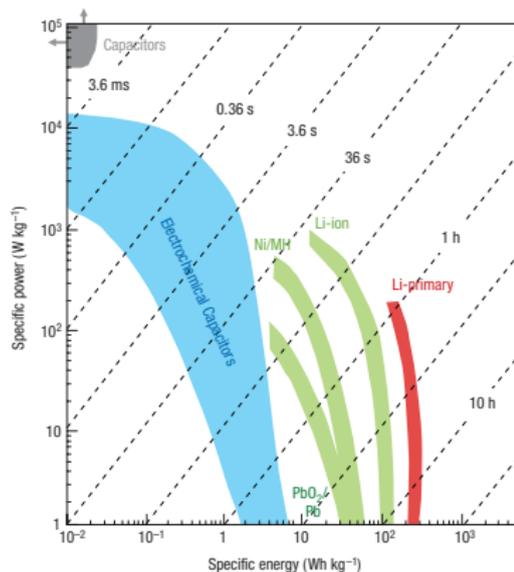


Much research work to be done in **materials** and **electrochemistry**, but...

Challenges

Need for improvements:

- Increase of capacitance
→ design of new carbon materials
- Electrolytes with high potential window
- Electrolytes with high conductivity at low temperature (-40°C)

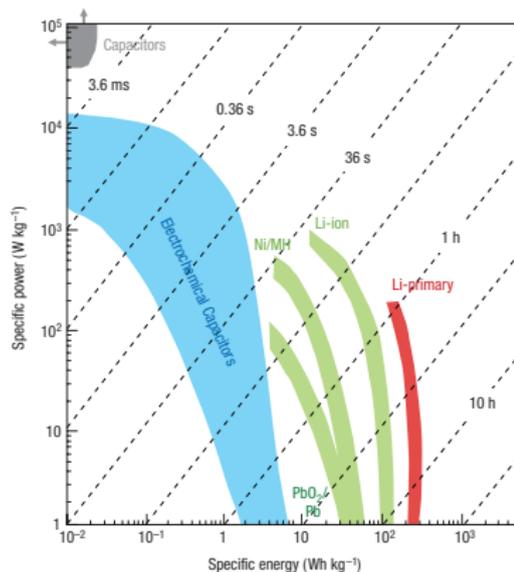

Much research work to be done in **materials** and **electrochemistry**, but...

- Local structure of the liquid inside the nanopores is unknown
- Very difficult to probe it experimentally

→ **Simulation can help!**

Outline

- 1 Supercapacitors
- 2 Molecular simulations**
- 3 Molecular origin of supercapacitance
- 4 Conclusion

Simulation method: molecular dynamics

- System of N classical atoms/molecules interacting together
- Periodic boundary conditions
- Iterative integration of Newton's equation

$$m^i \frac{\partial^2 \vec{r}^i}{\partial t^2} = \sum_{j \neq i} \vec{F}^{j \rightarrow i} = - \frac{\partial V}{\partial \vec{r}^i}$$

where V is the **interaction potential**

- Numerical resolution
- Trajectory of the atoms over several nanoseconds
- Determination of **structural**, **thermodynamic** and **transport** properties


Electrolyte: coarse-grained model

BMI⁺: 1-butyl-3-methylimidazolium

→ 3 sites

PF₆⁻: hexafluorophosphate

→ 1 site

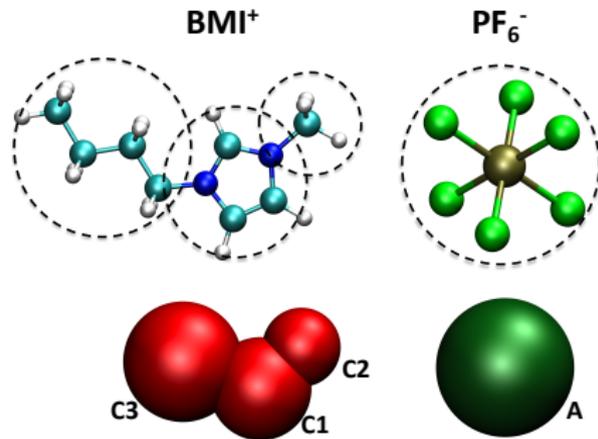


Interaction potential:

$$V = \sum_{i,j>i} \left[4\epsilon_{ij} \left(\left(\frac{\sigma_{ij}}{r_{ij}} \right)^{12} - \left(\frac{\sigma_{ij}}{r_{ij}} \right)^6 \right) + \frac{q_i q_j}{r_{ij}} \right]$$


Roy & Maroncelli, *J. Phys. Chem. B* **114**, 12629 (2010)

Merlet, Salanne & Rotenberg, *J. Phys. Chem. C* **116**, 7687 (2012)


Simulating constant voltage electrodes

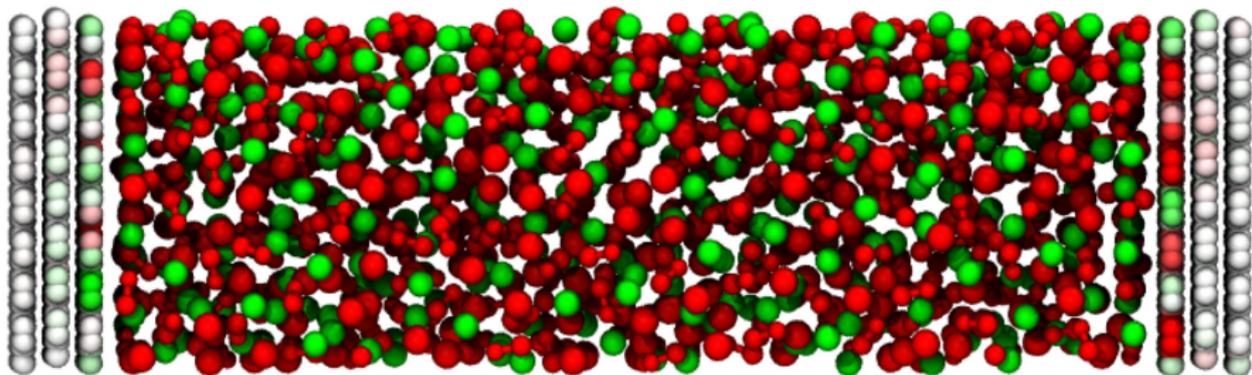


Simulating constant voltage electrodes

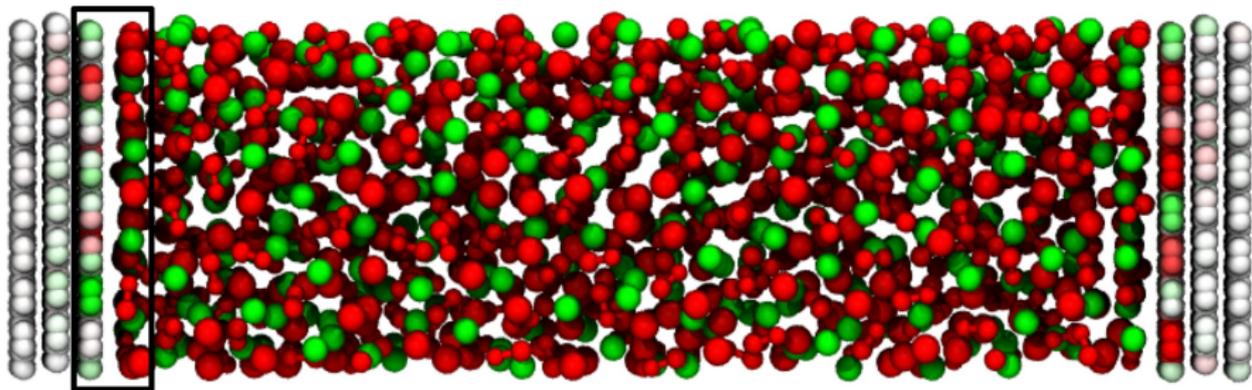


Simulating constant voltage electrodes

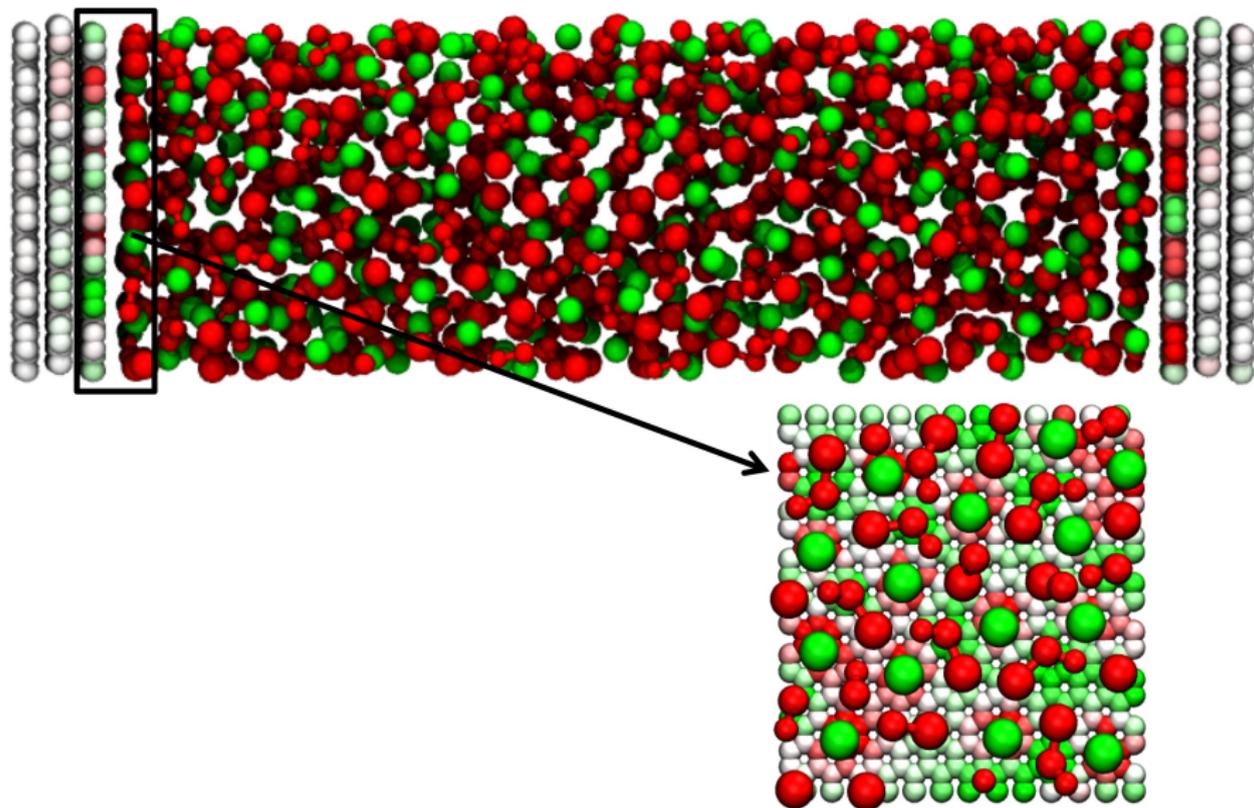

Simulating constant voltage electrodes

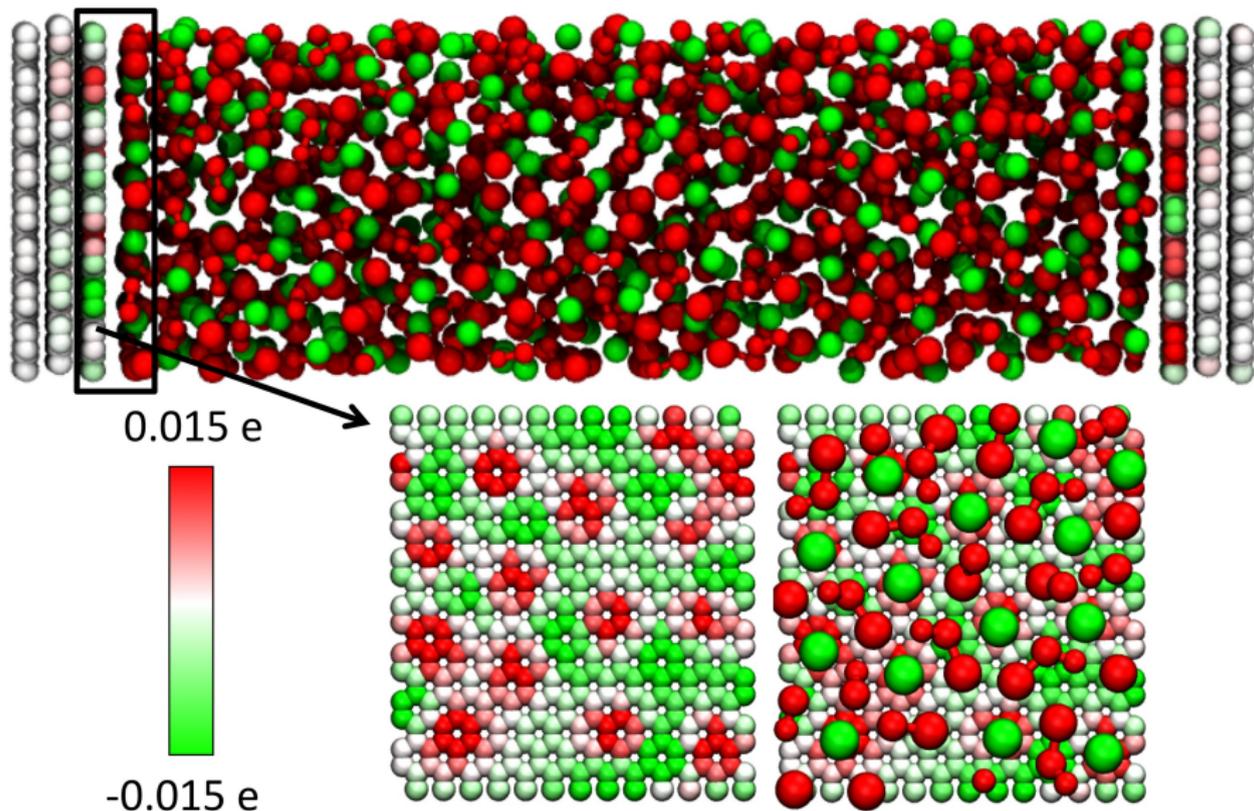

Porous electrodes: CDC model structures

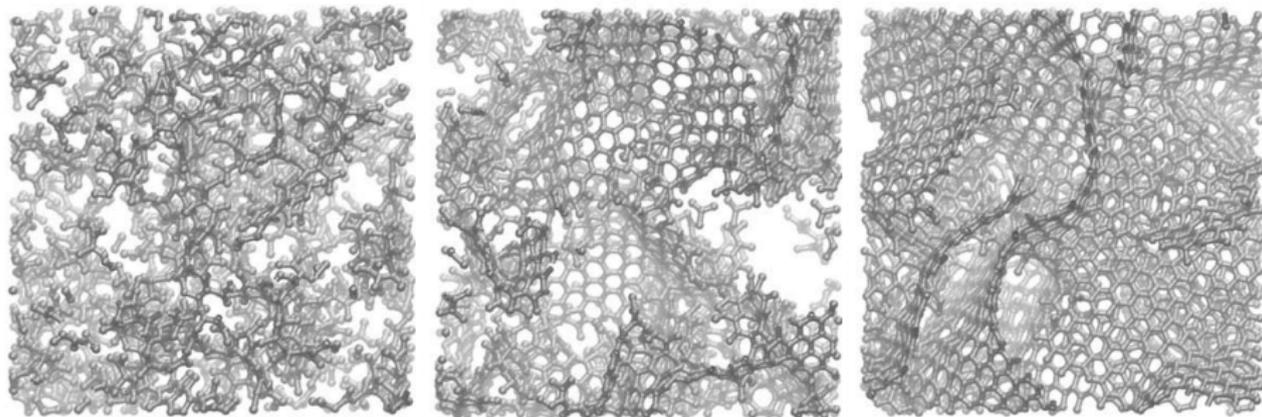

- Obtained from quenching a liquid carbon (ReaxFF)
- Different quenching rates: changes in the pore shape and size distribution
- Mimics CDC structures obtained at different temperatures

Example of trajectory


Loading movie

Simulation cell with 2-Dimensional periodic boundary conditions

Outline

- 1 Supercapacitors
- 2 Molecular simulations
- 3 Molecular origin of supercapacitance**
- 4 Conclusion


Increase of the capacitance in nanoporous carbons

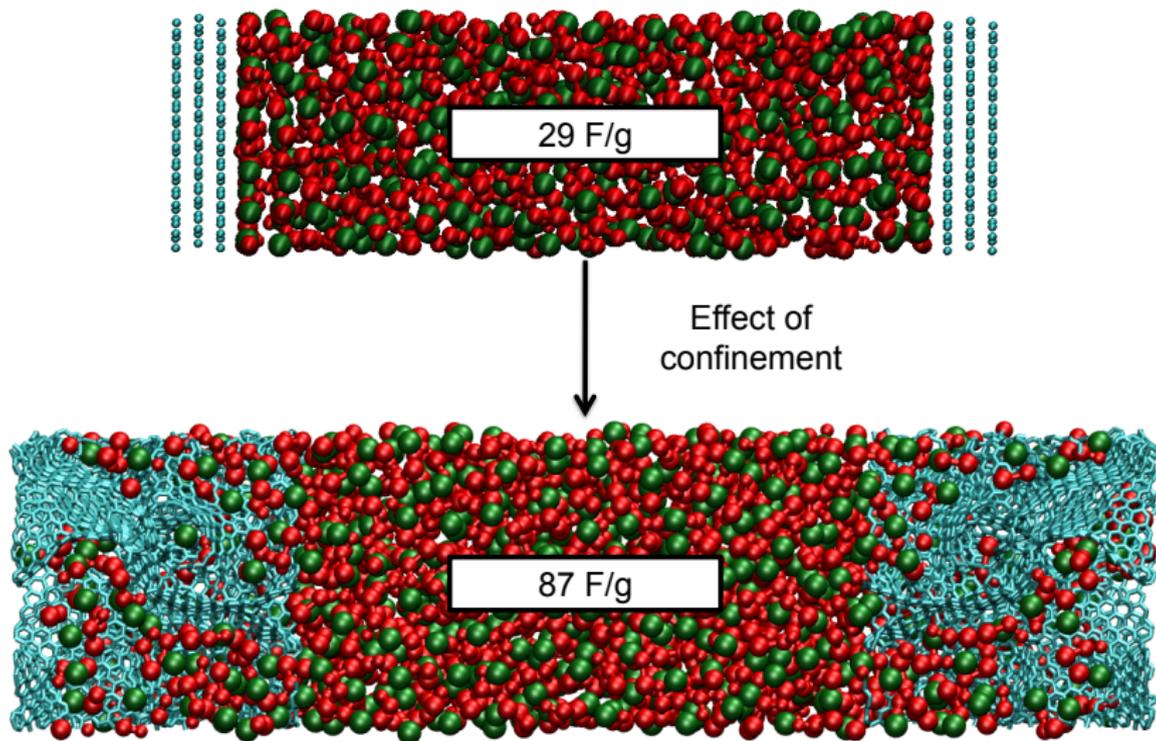

Merlet *et al.*, *Nature Materials*, 11, 306 (2012)

Superionic state


$\Psi = -0.5 \text{ V}$

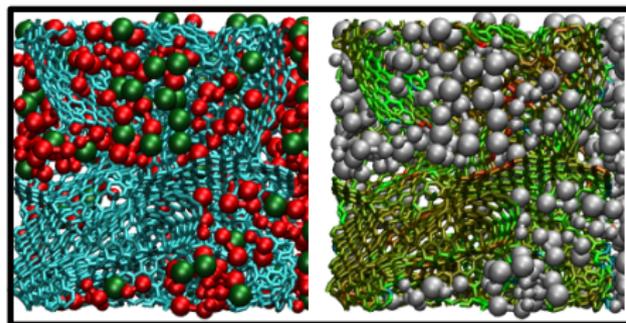

$N_+ = 104$

$N_- = 55$

$\Psi = +0.5 \text{ V}$

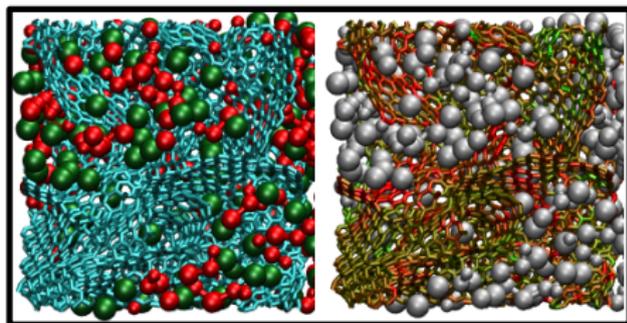


$N_+ = 66$

$N_- = 115$

Like-like ions interactions screened by the metallic walls
→ superionic state (Kornyshev)



NMR experiments on supercapacitors

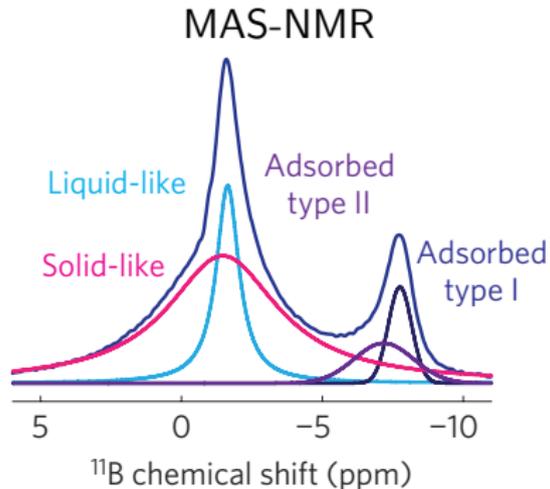

- Several adsorption modes

Deschamps *et al.*, *Nature Materials* **11**, 306 (2013)

NMR experiments on supercapacitors

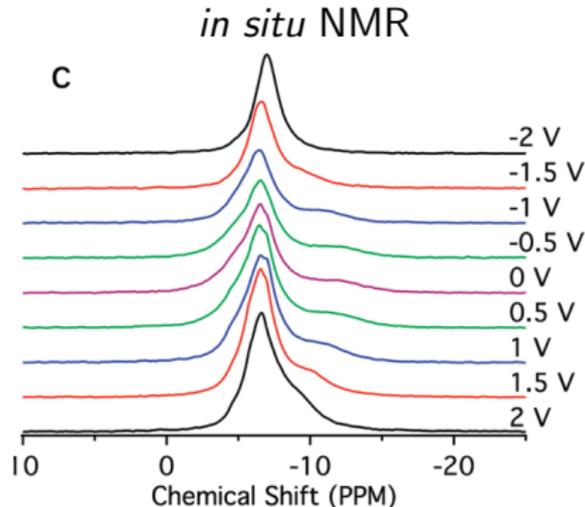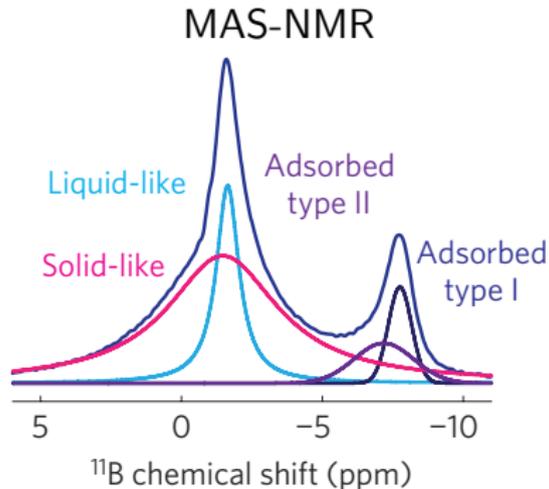


- Several adsorption modes
- Evolution with applied potential

Deschamps *et al.*, *Nature Materials* **11**, 306 (2013)


Wang *et al.*, *J. Am. Chem. Soc.* **133**, 19270 (2011)

A variety of adsorption sites


$$[\text{BMI}][\text{PF}_6] / \Delta\Psi = 0.0\text{V}$$

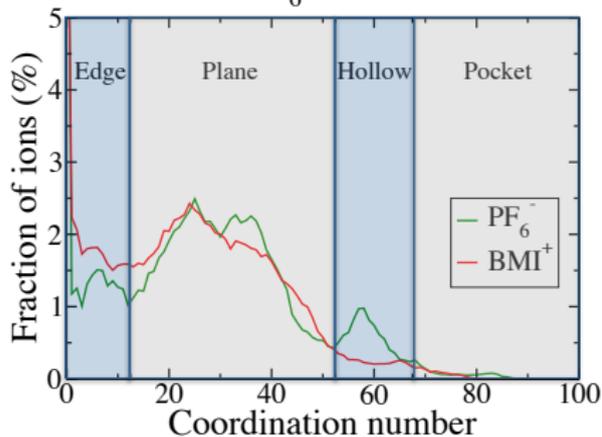


$$\text{ACN}-[\text{BMI}][\text{PF}_6] / \Delta\Psi = 0.0\text{V}$$

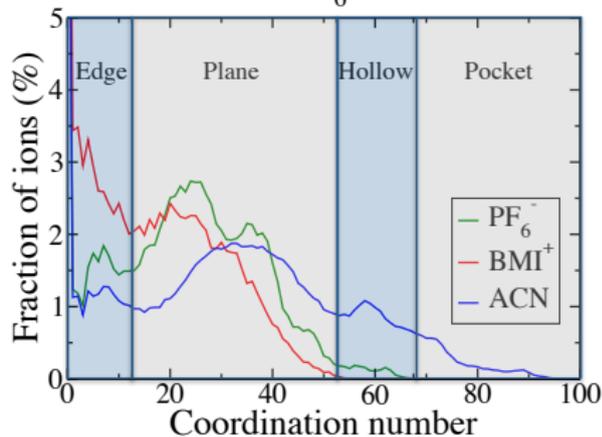


Edge

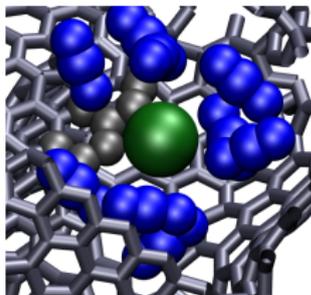


Plane

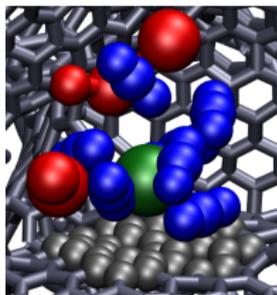


Hollow

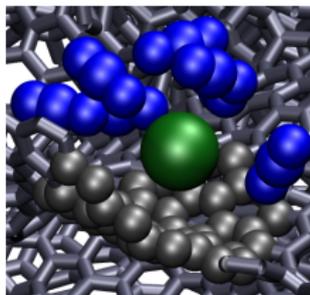

Pocket

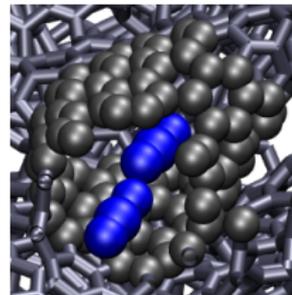


Evolution with applied potential


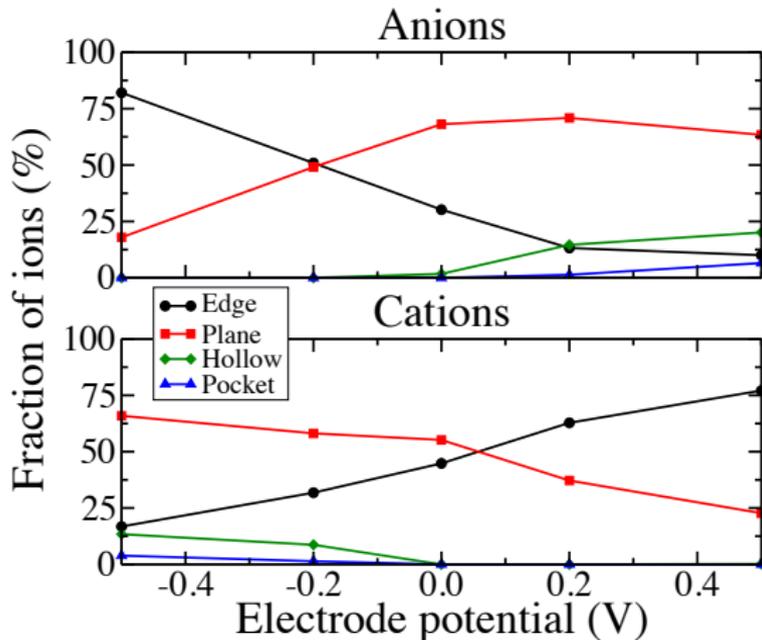


- Counter-ions migrate in confined sites...
- ... While other ions (and the solvent) leave them

Impact of local morphology on supercapacitor properties




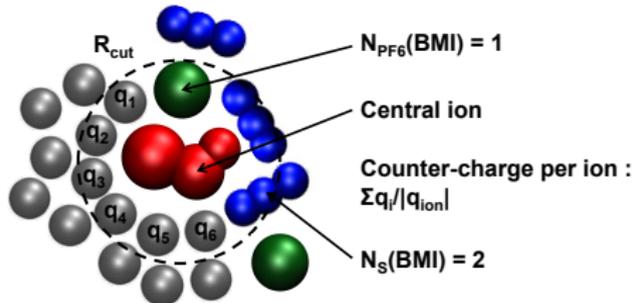


The local charge on the electrode is greater in highly confined sites

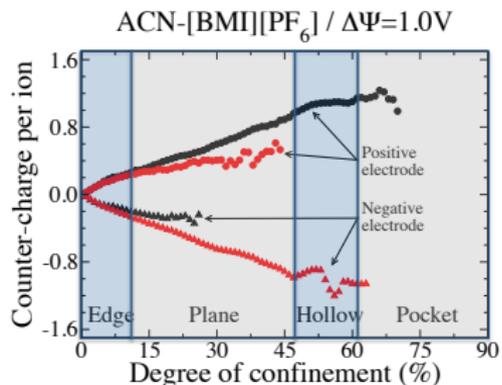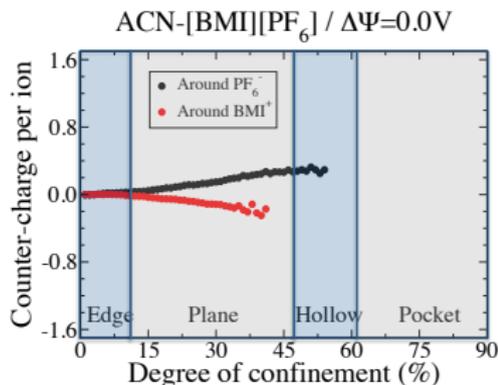

Merlet *et al.*, *Nature Communications*, 4, 2701 (2013)

Desolvation of ions in nanoporous carbons

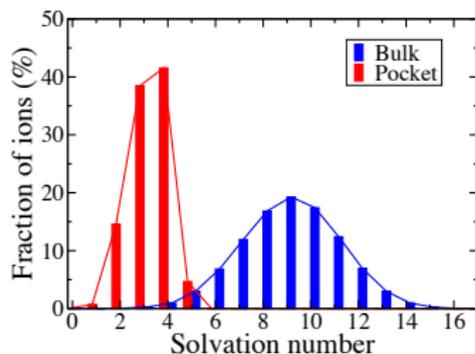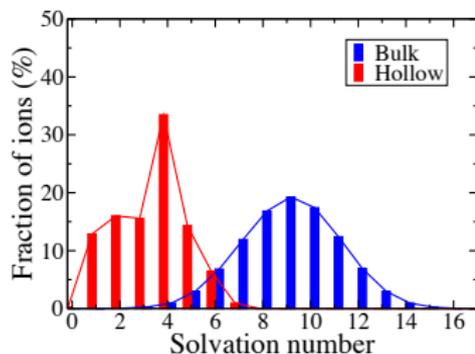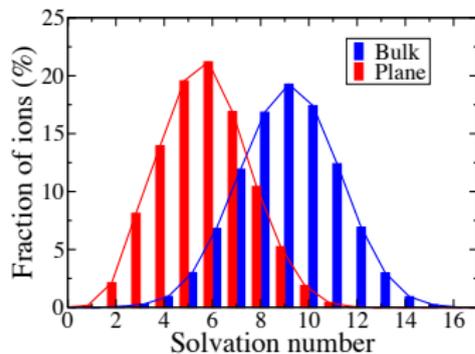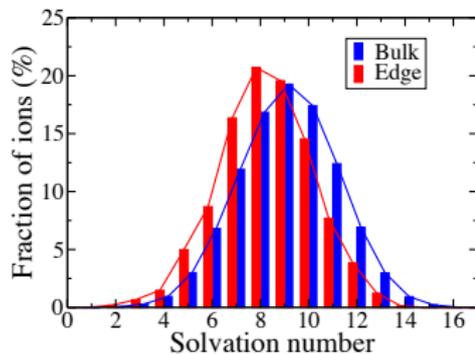

Merlet *et al.*, *Nature Communications*, 4, 2701 (2013)

Outline

- 1 Supercapacitors
- 2 Molecular simulations
- 3 Molecular origin of supercapacitance
- 4 Conclusion

Conclusion & Perspectives

- Simulations performed at constant applied potential
 - Realistic structures of CDCs
 - Nanoporous carbons:
 - screening by the metallic walls → superionic state
 - absence of overscreening due to confinement → better efficiency
 - role of the local morphology
 - Simulations of charge/discharge processes
-
- Influence of the ionic sizes (development of new models)
 - Porous carbon structure (evaluation of new models)
 - Ionic liquids dissolved in other solvents

Acknowledgements

- Céline Merlet, Clarisse Péan, Benjamin Rotenberg (PHENIX)
- Paul Madden (Oxford University)
- Patrice Simon (Université Paul Sabatier)
- Yury Gogotsi (Drexel University)
- French National Research Agency
- European Research Council (P. Simon project)
- CINES (project c2013096728)
- PRACE (project 2012071287)